

PACS: 71.36.+c, 78.20.-e, 78.68.+m

Reststrahlen spectroscopy of MgAl_2O_4 spinel

N.N. Boguslavskaya¹⁾, E.F. Venger¹⁾, N.M. Vernidub²⁾, Yu.A. Pasechnik²⁾, K.V. Shportko²⁾

¹⁾ Institute of Semiconductor Physics, NAS of Ukraine, 45 prospect Nauky, 03028 Kyiv, Ukraine

Phone: +380 (44) 265 6205; fax: +380 (44) 265 5430

²⁾ M.Dragomanov National Pedagogic University, 9 Pirogova St., 01030 Kyiv, Ukraine

Phone: +380 (44) 224 6557; fax: +380 (44) 224 2251

Abstract. Using IR reflectance spectroscopy and surface polariton spectroscopy in the reststrahlen region, we investigated Czochralski-grown MgAl_2O_4 spinel. The computer analysis of variance made for spectra enabled us to get a mathematical model for reflection spectra of spinel. In our calculations we used consistent data for optical parameters (zero- and high-frequency permittivities, transverse optical phonon frequencies and corresponding damping coefficients) of spinel single crystals that have been obtained from comparison between the measured and calculated spectra. These data were used when studying attenuated total reflection spectra and dispersion curves for surface polaritons in MgAl_2O_4 spinel.

Keywords: reflectance spectroscopy, surface polaritons, spinel, reststrahlen, attenuated total reflection spectra.

Paper received 27.11.01; revised manuscript received 18.01.02; accepted for publication 05.03.02.

1. Introduction

Both natural and synthetic spinelides are promising materials for use in micro- and optoelectronics. That is why they often draw attention of researchers. However, investigation of their physico-chemical properties is complicated by the fact that in many cases their structure is unknown. The attempts to make the problem easier by arranging the samples studied in series of pseudo-binary solid solutions often have not met with success. The reason for this lies in the fact that there are some restrictions on compatibility, heterogeneity and multicomponent character of isomorphous mixtures.

Many authors have dealt with investigation of IR absorption spectra of natural and synthetic chemical compounds of spinel-like structure (see the review [1]). In [1] these spectra were studied in spinelides belonging to the set of $(\text{Mg}, \text{Fe})(\text{Fe}^{3+}, \text{Al}, \text{Cr})_2\text{O}_4$ solid solutions. The authors of [1] have obtained both structural and spectroscopic characteristics of synthetic spinelides and proved, on the empirical level, that the model for independent vibrations of tetrahedral and octahedral “mol-

ecules” of spinel structure is inadequate. A comparison between the crystal-chemical and optical parameters of spinelides belonging to nine continuous sets of solid solutions enabled the authors of [1] to treat the spectra as resulting from vibrations of the spinelide lattice as a whole. The predominant role of the effect of octahedral isomorphous substitutions on the absorption spectral line positions also has been stressed in [1].

The MgAl_2O_4 spinel structure is typical for the $\text{X}^{2+}\text{Y}_2^{3+}\text{O}_4^{2-}$ -type compounds where X and Y are cations (at least one of which belongs to the transition element group) and O is oxygen [2]. For the so-called normal spinels the cation X is bivalent (Mg^{2+} , Mn^{2+} , Fe^{2+} , Ni^{2+} , Zn^{2+}), while cation Y is trivalent (Al^{3+} , V^{3+} , Cr^{3+} , Fe^{3+} , Mn^{3+}). The crystal has a face-centered cubic (FCC) lattice. The anions (located at vertexes) form the closest cubic three-layer package. One may recognize the following two cation sublattices in the spinel structure: tetrahedral (A-sublattice) and octahedral (B-sublattice). Chemical bonding in the spinel structure is of mixed ionic-covalent type. In *normal* spinels the cations X^{2+} occupy the tetrahedral (A) interstitials, while the cations Y^{3+}

occupy the octahedral (B) ones. In this case the chemical formula X²⁺Y₂³⁺O₄²⁻ is valid. The MgAl₂O₄ spinel belongs to normal, while MgFe₂O₄, Fe₃O₄ belong to *inverse* spinels. The spinel structure is like to that of the Fe₃O₄ magnetite: the Mg²⁺ ions occupy the tetrahedral interstitials and the Al³⁺ ions are located at the octahedral sites.

Highly symmetric (*Fd3m*) structure of cubic spinelides results in a rather simple form of IR absorption spectrum in the 200-1000 cm⁻¹ region. Depending on the compound studied and sample origin, this spectrum usually involves from two to four intense bands and a variable number of weaker bands that manifest themselves as “shoulders” at the intense band slopes.

After 1955, interpretation of the IR spectra in compounds of spinel structure is based on a theory that has been initially advanced by Waldron [3]. In his model the crystal structure considered has a rhombohedral primitive cell. In the case of normal spinel this cell contains two AO₄ tetrahedrons (each having four oxygen ions and a tetrahedral cation A at its center) and a tetrahedron B (that involves four octahedral cations). The vibrations of each of the above groups of ions have been classified according to the features of the point group *T_d* (which is believed to correspond to vibrations of the crystal as a whole). As a result, Waldron has concluded that only four crystal vibrational modes are IR-active. Two of them (having the highest frequencies ν_1 and ν_2) stem from oxygen ion motion, while the other two modes are related to motion of metal cations.

Comprehensive experimental studies of spinel IR spectra have been performed after the paper [3] by Waldron has appeared. Their results have been evidence in favor of existence of four fundamental absorption bands in the cubic spinel-type compounds. Indeed, four bands were observed. They were accompanied by weaker bands and inflections (“shoulders”) [3]. In two or three cases it was possible to relate some of these weaker bands and “shoulders” to presence of structural imperfections in the crystals studied, but generally their nature remained unclear.

An alternative approach to the problem of spectra interpretation has been advanced in [3]. The experimentally observed spectral features have been explained in terms of vibrations of crystal as a whole. It was shown that IR absorption in MgAl₂O₄ could be rather adequately described with a spectrum whose peaks were related to the critical points in the Brillouin zone.

Three intense bands (at frequencies of 692, 526 and 307 cm⁻¹) are observed in the IR absorption spectrum of synthetic MgAl₂O₄ spinel, along with a weaker peak or “shoulder” at a frequency of 720 cm⁻¹ (see Table 1). The experiments for a set of spinels where MgAl₂O₄ is a principal component showed that two other important frequencies also lie near 570 and 455 cm⁻¹. The observed spectrum features might depend on the preparation technique and material stoichiometry.

The absorption spectrum of the natural spinel is known to slightly differ from that of the synthetic material [3]. A comparison between the data for synthetic and natural

Table 1. IR absorption spectra of MgAl₂O₄ spinel [3].

Spectral feature	Frequency ν , cm ⁻¹ (a)		Frequency ν , cm ⁻¹ (c)	
	Synthetic spinel	Synthetic spinel	Natural spinel	Natural spinel
“Shoulder”	720	750	752	760
Peak	692	690	685	688
“Shoulder”	570	-	578	580
Peak	526	538	521	522
“Shoulder”	455			
Peak	307			309

[a] - X.W. Grimes, A.J. Collett // *phys. status solidi (b)* **43**, p. 591 (1971).

[b] - S. Hafner, F. Laves // *Z. Krist.* **115**, p. 321 (1961).

[c] J. Preudhomme, P. Tarte // *Spectrochim. Acta* **27A**, p. 1817 (1971).

spinel published by different authors is given in Table 1. The features of reflection spectrum for the natural MgAl₂O₄ single crystal published in 1964 by Slack [4] are also of interest; they are given in Table 2.

Table 2. Reflection spectrum of MgAl₂O₄ spinel natural single crystal [4].

Spectral features	Energy, eV	Frequency, cm ⁻¹
Weak “shoulder”	0.104	840
Sharp peak	0.091	735
“Shoulder”	0.072	582
Broad peak	0.066	533
“Shoulder”	0.059	477
Sharp peak	0.0375	304

For spinel whose primitive unit cell contains 14 ions 42 branches are to exist for the phonon dispersion. Thus, the problem of adequate interpretation of IR spectra is rather complicated due to the lack of additional information concerning the phonon dispersion curves. Since the ordinary unit cell of spinel belongs to the cubic (FCC) lattice, the Brillouin zone for spinel is similar to that of sphalerite (zinc blende) [4]. Therefore the phonon wave vectors at critical points are known.

The author of [4] has measured optical reflection from MgAl₂O₄ and FeAl₂O₄ in the 0.03 up to 2.0 eV range to determine the strong lattice absorption region and obtain reflection coefficient *R*. The measurements have been performed at a temperature of 300 K and almost normal incidence of light beam. Intense peaks of lattice absorption have been found in the photon energy range from 0.03 to 0.11 eV. The MgAl₂O₄ sample used was a natural spinel crystal from Burma; it was pale-rose colored. The synthetic FeAl₂O₄ crystal has been grown without additional annealing. The crystal surfaces were polished in such a way as to be optically flat for reflection measurements.

The results of MgAl₂O₄ reflection spectrum recording are shown in Fig. 1. The principal lattice absorption peaks lie at 0.066 and 0.091 eV (533 and 735 cm⁻¹).

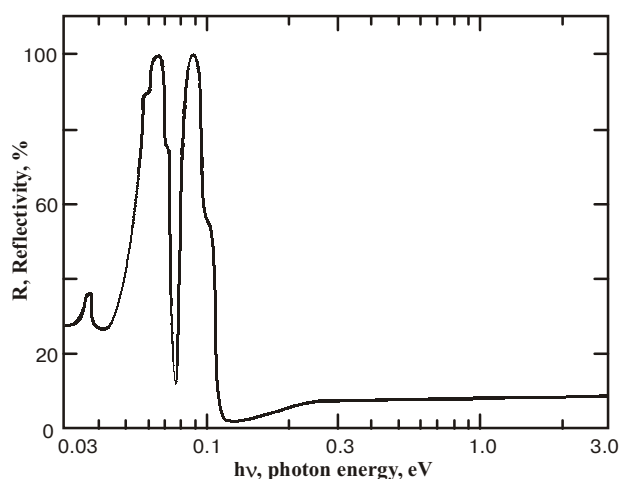


Fig. 1. Reflection spectrum of MgAl₂O₄ spinel natural single crystal [4].

The data on other (less intense) peaks obtained are given in Table 3. The values of MgAl₂O₄ reflection coefficient *R* at normal incidence of light beam onto the sample (Table 3) are believed to be rather accurate [4]. The values of *R* for FeAl₂O₄ recorded at angle of incidence equal to 30° are approximate, but they still give relative intensities of different peaks.

The intense reflection peaks are related to strong absorption. There is close similarity between these lattice vibrational peaks for MgAl₂O₄ and FeAl₂O₄ because both crystals belong to the spinel structure and their lattice parameters are almost the same. A Fe atom is heavier than a Mg one; the FeAl₂O₄ reflection peaks lie at energies that are below those in MgAl₂O₄ by about 5%. The reflection coefficient *R* for MgAl₂O₄ is very low (from 2 to 8%) in the energy range from 0.12 to 3.0 eV (actually up to 4 eV). The overall situation for FeAl₂O₄ is similar.

Optical properties of spinel that served as substrate when growing silicon layers were studied in [5]. The MgAl₂O₄ substrate was Czochralski-grown; it had the

Table 3. Reflection spectrum of MgAl₂O₄ spinel natural single crystal [4]. (Greek letters are used for absorption bands labeling.)

Band label	Energy, eV	Frequency, cm ⁻¹	Reflection coefficient <i>R</i> , %	Spectral features
α	0.0375	303	36	Broad peak
β	0.059	476	89	Sharp peak
γ	0.066	533	100	Broad peak
δ	0.072	581	75	“Shoulder”
ϵ	0.091	735	100	Sharp peak
ζ	0.104	840	50	Slightly pronounced “shoulder”
θ	0.176		Low	

structure of normal cubic spinel. Two principal MgAl₂O₄ absorption bands (lying at 688 and 522 cm⁻¹) have been identified. They are related to the O-Al complex in the octahedron.

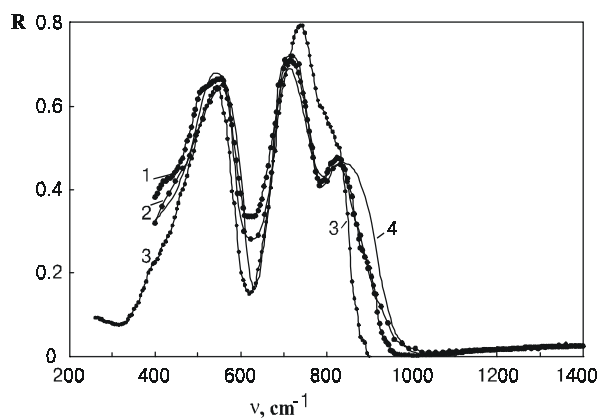


Fig. 2. Reflection spectra of MgAl₂O₄ spinel synthetic single crystals: 1, 2 – experimental spectra for two samples; 3 – spectrum taken from [5]; 4 – calculated spectrum with parameters *R*(ν) given in Table 4.

2. Results and discussion

Here we present some results of our experiments dealing with the optical properties of Czochralski-grown synthetic MgAl₂O₄ spinel. We used IR reflectance spectroscopy and surface polariton spectroscopy in the reststrahlen region. The IR reflection spectra in the 400-1400 cm⁻¹ range were taken with spectrometer IKS-29 (equipped with attachment IPO-22) using polarized radiation. These spectra (Fig. 2, curves 1, 2) somewhat differ from those given in [5]. The reflection peaks taken in [5] (see Fig. 2, curve 3) lie at frequencies of 745 and 545 cm⁻¹. They refer to the same lattice vibrations as the absorption peaks. The reflection peaks are shifted toward higher frequencies as compared to the absorption peaks. This is characteristic of strong absorption bands. The reflection coefficient *R* = 0.13 in the 0.3-3 μ m wavelength range leads to the refraction index value *n* = 1.7. This value agrees with those (1.7-1.72) obtained in a number of papers at a wavelength of 0.6 μ m. From the interference fringes observed in experiments with spinel transparency it follows that the refraction index value is close to 3; at low (near 1 kHz) frequencies the spinel permittivity is 8.4.

A comparison between the MgAl₂O₄ reflection spectra obtained in [4] and [5] evidences that they differ substantially. In [4] it was stated that the reflection spectrum has two peaks corresponding to total (100%) reflection. Contrary to this, the reflection peaks at frequencies of 745 and 545 cm⁻¹ obtained in [5] corresponded to reflection coefficient of about 80% and 65%, respectively. No model has been advanced in either [4] or [5] that could give a quantitative description for the spinel reststrahlen region.

Table 4. Optical parameters of the reflection spectra model R(ν) and ATR for spinel.

	ϵ_0	ϵ_∞	ν_{T1} cm ⁻¹	ν_{T2} cm ⁻¹	ν_{T3} cm ⁻¹	γ_{T1} cm ⁻¹	γ_{T2} cm ⁻¹	γ_{T3} cm ⁻¹	b_1	b_2	b_3
R(ν)	7.4	2.89	510	680	795	5	1.4	16	3.58	0.73	0.2
ATR	7.4	2.89	502	650	830	65	20	136	3.58	0.73	0.2

A computer analysis of variance made for the spectra obtained enabled us to advance a mathematical model for spinel reflection spectra. In our calculations we used the consistent data on the optical parameters of spinel single crystals that were obtained by comparing the experimental and calculated spectra.

When calculating the reflection coefficient, we used the following well-known expression [6]:

$$R(\nu) = \frac{\sqrt{\epsilon_1^2 + \epsilon_2^2} - \sqrt{2(\sqrt{\epsilon_1^2 + \epsilon_2^2} + \epsilon_1)} + 1}{\sqrt{\epsilon_1^2 + \epsilon_2^2} + \sqrt{2(\sqrt{\epsilon_1^2 + \epsilon_2^2} + \epsilon_1)} + 1} \quad (1)$$

Here ϵ_1 and ϵ_2 are, respectively, the real and imaginary parts of the crystal permittivity that was taken in the following form:

$$\epsilon(\nu) = \epsilon_1 + i\epsilon_2 = \epsilon_\infty + \sum_{i=1}^3 \frac{S_i \nu_{Ti}^2}{\nu_{Ti}^2 - \nu^2 - i\gamma_{Ti}\nu} \quad (2)$$

Here ϵ_∞ is the high-frequency permittivity; S_i is the i -th oscillator strength; ν_{Ti} (γ_{Ti}) is the frequency (damping coefficient) of the i -th oscillator, i.e., transverse optical phonon. The summation is made for the case of a multiphonon vibrational system of the crystal lattice. A root-mean-square deviation d of the experimental parameter value from the calculated one is determined from the

formula $\delta = [\sum_{i=1}^N (R_{Ei} - R_{Ti})^2]^{1/2}/N$. Here R_{Ei} (R_{Ti}) is the experimental (theoretical) reflection coefficient value at the i -th point of the spectrum; N is the number of points of the spectrum.

The curves 1, 2 in Fig. 2 correspond to the experimental reflection spectra of synthetic MgAl₂O₄ spinel. These spectra have been compared to the theoretical one (curve 4) using analysis of variance. This enabled us to develop a mathematical model for the reflection spectra of MgAl₂O₄ spinel. These spectra are of the form that is characteristic of the normal spinel, namely, two peaks at frequencies of 560 and 720 cm⁻¹ and an inflection (“shoulder”) at a frequency of 820 cm⁻¹. The reflection coefficient at frequencies over 1000 cm⁻¹ is $R(\nu) \leq 0.13$. A comparison has shown that the calculated spectra differed from the experimental ones by 0.6% (at parameters that are given below).

According to the developed model, the phonon system of the crystals studied may be described with three resonance frequencies (510, 680 and 790 cm⁻¹); the corresponding oscillator strengths and damping coefficients

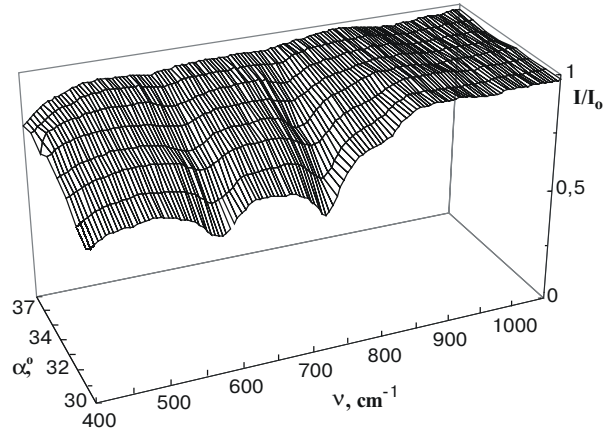


Fig. 3. Experimental SP ATR spectra of MgAl₂O₄ spinel synthetic single crystal (curves 1, ..., 8 have been taken at reflection angles of 30.3, ..., 39.3°).

are 0.58, 0.73, 0.2 and 5, 1.3, 19 cm⁻¹, respectively. Fig. 2 (curve 4) demonstrates a rather good agreement between the theoretical and experimental results at $\epsilon_0 = 7.4$ and $\epsilon_\infty = 2.89$; they also agree with the data given by other authors (see, for instance, [5]). The data obtained as a result of such comparison made it possible to study surface phonon polaritons in MgAl₂O₄ spinel.

At the moment there are a number of papers dealing with investigation of surface polaritons (SP) in such compounds as silicon carbide, aluminum oxide, etc. For spinels, however, the characteristics of SP in the IR region practically have not been studied yet [7, 8]. Here we present, for the first time, results of our investigations of surface phonon polaritons in MgAl₂O₄ spinel.

One of the experimental techniques used when studying SP is attenuated total reflectance (ATR). We took the ATR spectra of SP for Czochralski-grown synthetic MgAl₂O₄ spinel in the 400-1100 cm⁻¹ frequency range. In our experiments we used polarized radiation and spectrometer IKS-29 equipped with attachment NPVO-1. Shown in Fig. 3 is the so-called SP reflection surface, $R(\nu, \alpha)$. It is a set of eight experimental SP ATR spectra taken at angles from 30 up to 39°. A reflection surface $R(\nu, \alpha)$ is a three-dimensional presentation of the system transmission that depends on the radiation frequency ν and angle α (angle of incidence for an ATR unit).

If there are SP damping and dissipation of the electromagnetic wave energy, then the surface $R(\nu, \alpha) = I(\nu, \alpha)/I_0(\nu, \alpha)$ has two “canyons” connected with a “pass”.

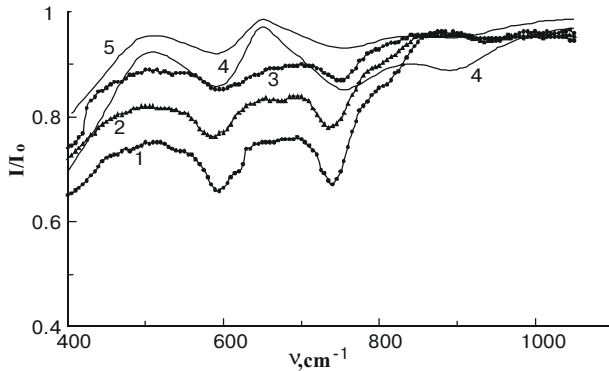


Fig. 4. Experimental ATR spectra of MgAl₂O₄ spinel single crystal: 1-3 – experiment, 4 and 5 - calculation; reflection angle α is 29.3° (1), 31.3° (2), 33.3° (3); 31.3° (4), 33.3° (5).

(Here $I(\nu, \alpha)$ is the intensity of radiation passing through the “ATR unit (semicylinder)-gap-sample” system; $I_0(\nu, \alpha)$ is the intensity of radiation incident onto the ATR unit.) The “canyon” depth depends on the system parameters: gap d_3 between the ATR semicylinder and sample, radiation frequency ν , complex permittivity $\epsilon(\nu, \kappa)$ of the sample, permittivities of the ATR unit and gap. The SP dispersion curves $\nu_s(k)$ correspond to the “canyons”, i.e., to the set of ATR spectra minima. (Here ν_s is the SP frequency and k is the SP wave vector.) The frequencies at which the minima of the experimentally determined surface $R(\nu, \alpha)$ lie, as a rule, agree with those of the calculated dispersion curve $\nu_s(k)$ at the phonon damping coefficient $\gamma_T = 0$.

The relation between the ATR spectrum minima and SP dispersion curve is given by the following equation:

$$k = (2\pi\nu/c)n \sin \alpha \quad (3)$$

Here ν is the frequency of the ATR spectrum minimum; c is the speed of light in a vacuum; n is the refractive index of material of the ATR semicylinder. (We used the material KRS-5 with $n = 2.37$.) If the optical phonon damping is taken into account, then one more “canyon” appears at the reflection surface $R(\nu, \alpha)$, with a “pass” to the first “canyon” in the frequency region $\nu > \nu_s$. This can be detected by recording the SP ATR spectra at $\nu = \text{const}$ and scanning over the angle α values.

Three experimental ATR spectra (curves 1-3) taken at angles $\alpha = 29.3, 31.3$ and 33.3° are shown in Fig. 4. Curves 4 and 5 are the theoretical ATR spectra calculated at $\alpha = 31.3$ and 33.3° ; the oscillation frequencies were 502, 650 and 830 cm^{-1} , while the damping coefficients were 65, 20 and 136 cm^{-1} .

Figure 5 presents the calculated (full curves) and experimental (dots) SP dispersion curves in spinel. The feature of dispersion curves in MgAl₂O₄ spinel is presence of three branches. This fact agrees with the developed mathematical model for spinel that takes into account contributions from three oscillators (phonons) to the permittivity. The obtained consistent data concerning the optical

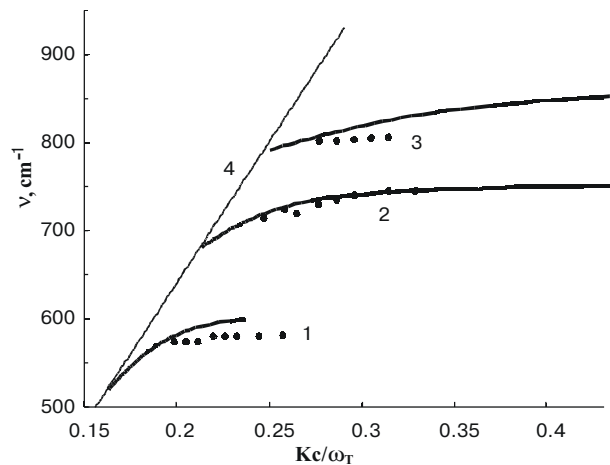


Fig. 5. SP dispersion curves for MgAl₂O₄ spinel single crystal: 1-3 – experiment (dots) and calculation at ATR model parameters given in Table 4; 4 – light curve.

parameters (zero- and high-frequency permittivities, transverse optical phonon frequencies and corresponding damping coefficients) of spinel single crystals are presented in Table 4.

The $R(\nu)$ row in Table 4 has been obtained from comparison between the experimental and calculated spectra. The ATR row gives the parameter values used when trying to simulate the calculated ATR spectra at $\alpha = 31.3$ and 33.3° . One can see from Fig. 4 that only qualitative agreement exists between the spectra 2, 3 and 4, 5. When comparing the data obtained from the $R(\nu)$ and ATR spectra, one can see that to get better agreement one should take essentially different frequencies of three oscillators, as well as the corresponding damping coefficients. In particular, the oscillator frequencies differ by 10-30 cm^{-1} and the damping coefficients differ by a factor of 10-15. This indicates at the effect of a near-surface layer on the properties of phonon SP in spinel. We propose to obtain the data concerning optical properties of near-surface regions from quantitative comparison between the experimental and theoretical reflection surfaces made using PC. This will make it possible to get more detailed information on the system studied.

3. Conclusion

Using IR reflectance spectroscopy and surface polariton spectroscopy in the reststrahlen region, we investigated Czochralski-grown MgAl₂O₄ spinel. The computer analysis of variance made for spectra enabled us to get a mathematical model for reflection spectra of spinel. In our calculations we used consistent data for optical parameters (zero- and high-frequency permittivities, transverse optical phonon frequencies and corresponding damping coefficients) of spinel single crystals that have been obtained from comparison between the measured and calculated spectra. These data were used when studying ATR spectra and dispersion curves for surface polaritons in MgAl₂O₄ spinel.

References

1. V.O. Khudolozhkin, G.A. Narnov, A.A. Karabtsov, M.I. Patuk, Vibrational spectra of solid solutions of (Mg, Fe)(Fe³⁺, Al, Cr)₂O₄ system spinelides // *Mineralogicheskii Zhurn.* **8**(2), pp. 17-23 (1986) (in Russian).
2. M.P. Shaskolskaya, *Crystallography*, Vysshaya Shkola, Moscow (1976) (in Russian).
3. N.W. Grimes, Interpretation of the infrared spectrum of spinels // *Spectrochim. Acta* **28A**, pp. 2217-2225 (1972).
4. G.A. Slack, FeAl₂O₄-MgAl₂O₄: Growth and some thermal, optical, and magnetic properties of mixed single crystals // *Phys. Rev.* **134**(5A), pp. 1268-1280 (1964).
5. H.J. Stein, Optical and electrical characteristics of MgO·Al₂O₃ spinel and silicon-on-spinel // *Solid St. Electronics* **15**, pp. 1209-1217 (1972).
6. Yu.I. Ukhanov, *Optical Properties of Semiconductors*, Nauka, Moscow (1977) (in Russian).
7. Yu.A. Pasechnik, Surface polaritons in silicon carbide, Chap. 14 in: *Problems of Semiconductor Surface Physics*, Naukova Dumka, Kiev (1981) (in Russian).
8. N.L. Dmitruk, V.G. Litovchenko, V.L. Strizhevskii, *Surface Polaritons in Semiconductors and Insulators*, Naukova Dumka, Kiev (1989) (in Russian).